REVISIONS

LTR	DESCRIPTION	DATE (YR-MO-DA)	APPROVED
A	Changes in accordance with NOR 5962-R213-97.	97-03-28	Monica L. Poelking
B	Changes in accordance with NOR 5962-R391-97.	97-07-25	Raymond Monnin
C	Incorporate revisions A and B. Update boilerplate to MIL-PRF-38535 requirements. Editorial changes throughout. – LTG	03-10-16	Thomas M. Hess
D	Update radiation features in section 1.5 and paragraphs 4.4.4.1 – 4.4.4.4. Update boilerplate paragraphs to the current MIL-PRF-38535 requirements. - LTG	10-04-19	Thomas M. Hess
E	Update radiation features in section 1.5. Update devices supplier information. Remove class M requirements throughout. Update boilerplate paragraphs to MIL-PRF-38535 requirements. - MAA	16-07-01	Thomas M. Hess
F	Update devices supplier CAGE 34371 information to bulletin page. Update boilerplate paragraphs to the current MIL-PRF-38535 requirements. - TTM	23-04-14	Muhammad A. Akbar

THE ORIGINAL FIRST SHEET OF THIS DRAWING HAS BEEN REPLACED.

Revision Status of Sheets

REV																						
SHEET																						
REV	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F		
SHEET	1	2	3	4	5	6	7	8	9	10	11	12	13	14	15	16	17	18	19	20		

PMIC N/A

STANDARD MICROCIRCUIT DRAWING

THIS DRAWING IS AVAILABLE FOR USE BY ALL DEPARTMENTS AND AGENCIES OF THE DEPARTMENT OF DEFENSE

PREPARED BY
Dan Wonnell

CHECKED BY
Monica L. Poelking

APPROVED BY
Monica L. Poelking

DRAWING APPROVAL DATE
95-12-05

DLA LAND AND MARITIME
COLUMBUS, OHIO 43218-3990
https://www.dla.mil/LandandMaritime

MICROCIRCUIT, DIGITAL, RADIATION HARDENED CMOS, 8-BIT ADDRESSABLE LATCH, MONOLITHIC SILICON

AMSC N/A	REVISION LEVEL F	SIZE A	CAGE CODE **67268**	**5962-96615**


SHEET 1 OF 20

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

1. SCOPE

1.1 Scope. This drawing documents two product assurance class levels consisting of high reliability (device classes Q) and space application (device class V). A choice of case outlines and lead finishes are available and are reflected in the Part or Identifying Number (PIN). When available, a choice of Radiation Hardness Assurance (RHA) levels is reflected in the PIN.

1.2 PIN. The PIN is as shown in the following example:

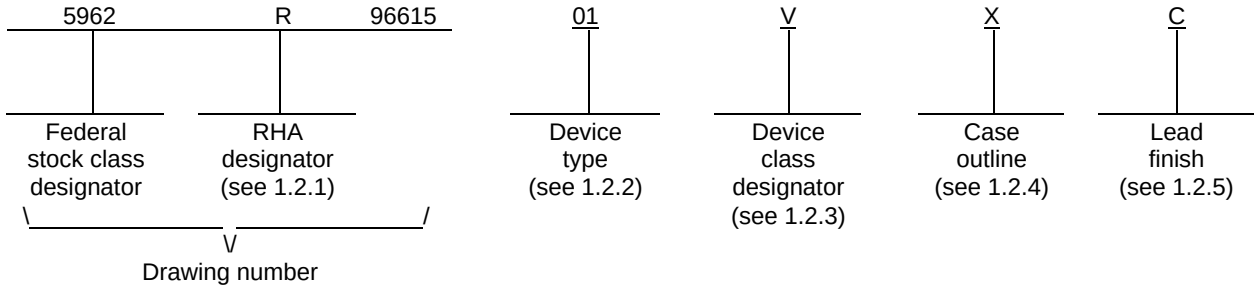

1.2.1 RHA designator. Device classes Q and V RHA marked devices meet the MIL-PRF-38535 specified RHA levels and are marked with the appropriate RHA designator. A dash (-) indicates a non-RHA device.

1.2.2 Device type(s). The device type(s) identify the circuit function as follows:

Device type	Generic number	Circuit function
01	4099B	Radiation hardened CMOS, 8-bit addressable latch

1.2.3 Device class designator. The device class designator is a single letter identifying the product assurance level as follows:

Device class	Device requirements documentation
Q or V	Certification and qualification to MIL-PRF-38535

1.2.4 Case outline(s). The case outline(s) are as designated in MIL-STD-1835 and as follows:

Outline letter	Descriptive designator	Terminals	Package style
E	CDIP2-T16	16	Dual-in-line
X	CDFP4-F16	16	Flat pack

1.2.5 Lead finish. The lead finish is as specified in MIL-PRF-38535 for device classes Q and V.

1.3 Absolute maximum ratings. 1/ 2/ 3/

Supply voltage range (V_{DD})	-0.5 V dc to +20 V dc
Input voltage range	-0.5 V dc to V_{DD} + 0.5 V dc
DC input current, any one input	±10 mA
Device dissipation per output transistor	100 mW
Storage temperature range (T_{STG})	-65°C to +150°C
Lead temperature (soldering, 10 seconds)	+265°C
Thermal resistance, junction-to-case (θ_{JC}):	
Case E	24°C/W
Case X	29°C/W
Thermal resistance, junction-to-ambient (θ_{JA}):	
Case E	73°C/W
Case X	114°C/W
Junction temperature (T_J)	+175°C
Maximum power dissipation at T_A = +125°C (P_D): 4/	
Case E	0.68 W
Case X	0.44 W

1.4 Recommended operating conditions.

Supply voltage range (V_{DD})	3.0 V dc to +18 V dc
Case operating temperature range (T_C)	-55°C to +125°C
Input voltage (V_{IN})	0 V to V_{DD}
Output voltage (V_{OUT})	0 V to V_{DD}

1.5 Radiation features.

Maximum total dose available (dose rate = 50 - 300 rads(Si)/s) .....100 krads(Si) 5/

Single event phenomenon (SEP):

No SEL occurs at effective LET (see 4.4.4.4)	≤ 75 MeV/(cm²/mg) 6/
No SEU occurs at effective LET (see 4.4.4.4)	≤ 75 MeV/(cm²/mg) 6/

1/ Stresses above the absolute maximum rating may cause permanent damage to the device. Extended operation at the maximum levels may degrade performance and affect reliability.

2/ Unless otherwise specified, all voltages are referenced to V_{SS}.

3/ The limits for the parameters specified herein shall apply over the full specified V_{DD} range and case temperature range of -55°C to +125°C unless otherwise noted.

4/ If device power exceeds package dissipation capability, provide heat sinking or derate linearly (the derating is based on θ_{JA}) at the following rate:

Case E	13.7 mW/°C
Case X	8.8 mW/°C

5/ The manufacturer supplying device type 01 has performed characterization testing in accordance with MIL-STD-883 method 1019 condition A to a maximum total dose of 100 krads(Si). The radiation end point limits for the noted parameters are guaranteed only for the conditions as specified in MIL-STD-883, method 1019, condition A to a maximum total dose of 100 krads(Si).

6/ Limits are guaranteed by design or process but not production tested unless specified by the customer through the purchase order or contract.

2. APPLICABLE DOCUMENTS

2.1 Government specification, standards, and handbooks. The following specification, standards, and handbooks form a part of this drawing to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

DEPARTMENT OF DEFENSE SPECIFICATION

MIL-PRF-38535 - Integrated Circuits, Manufacturing, General Specification for.

DEPARTMENT OF DEFENSE STANDARDS

MIL-STD-883 - Test Method Standard Microcircuits.
MIL-STD-1835 - Interface Standard Electronic Component Case Outlines.

DEPARTMENT OF DEFENSE HANDBOOKS

MIL-HDBK-103 - List of Standard Microcircuit Drawings.
MIL-HDBK-780 - Standard Microcircuit Drawings.

(Copies of these documents are available online at https://quicksearch.dla.mil/.)

2.2 Non-Government publications. The following document(s) form a part of this document to the extent specified herein. Unless otherwise specified, the issues of the documents are the issues of the documents cited in the solicitation or contract.

ASTM INTERNATIONAL (ASTM)

ASTM F1192 - Standard Guide for the Measurement of Single Event Phenomena (SEP) Induced by Heavy Ion Irradiation of Semiconductor Devices.

(Copies of these documents are available online at https://www.astm.org/.)

2.3 Order of precedence. In the event of a conflict between the text of this drawing and the references cited herein, the text of this drawing takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Item requirements. The individual item requirements for device classes Q and V shall be in accordance with MIL-PRF-38535 and as specified herein or as modified in the device manufacturer's Quality Management (QM) plan. The modification in the QM plan shall not affect the form, fit, or function as described herein.

3.1.1 Microcircuit die. For the requirements for microcircuit die, see appendix A to this document.

3.2 Design, construction, and physical dimensions. The design, construction, and physical dimensions shall be as specified in MIL-PRF-38535 and herein for device classes Q and V.

3.2.1 Case outlines. The case outlines shall be in accordance with 1.2.4 herein.

3.2.2 Terminal connections. The terminal connections shall be as specified on figure 1.

3.2.3 Timing diagram. The timing diagram shall be as specified on figure 2.

3.2.4 Radiation exposure circuit. The radiation exposure circuit shall be maintained by the manufacturer under document revision level control and shall be made available to the preparing and acquiring activity upon request.

3.3 Electrical performance characteristics and postirradiation parameter limits. Unless otherwise specified herein, the electrical performance characteristics and postirradiation parameter limits are as specified in table IA and shall apply over the full case operating temperature range.

3.4 Electrical test requirements. The electrical test requirements shall be the subgroups specified in table IIA. The electrical tests for each subgroup are defined in table IA.

3.5 Marking. The part shall be marked with the PIN listed in 1.2 herein. In addition, the manufacturer's PIN may also be marked. For packages where marking of the entire SMD PIN number is not feasible due to space limitations, the manufacturer has the option of not marking the "5962-" on the device. For RHA product using this option, the RHA designator shall still be marked. Marking for device classes Q and V shall be in accordance with MIL-PRF-38535.

3.5.1 Certification/compliance mark. The certification mark for device classes Q and V shall be a "QML" or "Q" as required in MIL-PRF-38535.

3.6 Certificate of compliance. For device classes Q and V, a certificate of compliance shall be required from a QML-38535 listed manufacturer in order to supply to the requirements of this drawing (see 6.6.1 herein). The certificate of compliance submitted to DLA Land and Maritime -VA prior to listing as an approved source of supply for this drawing shall affirm that the manufacturer's product meets, for device classes Q and V, the requirements of MIL-PRF-38535 and herein.

3.7 Certificate of conformance. A certificate of conformance as required for device classes Q and V in MIL-PRF-38535 shall be provided with each lot of microcircuits delivered to this drawing.

TABLE IA. Electrical performance characteristics.

Test	Symbol	Test conditions $-55°C \le T_C \le +125°C$ unless otherwise specified	Device type	Group A subgroups	Limits		Units
					Min	Max	
Supply current	I_{DD}	V_{DD} = 5 V V_{IN} = 0.0 V or V_{DD}	All	1, 3 1/		5.0	µA
				2 1/		150	
		V_{DD} = 10 V V_{IN} = 0.0 V or V_{DD}	All	1, 3 1/		10	
				2 1/		300	
		V_{DD} = 15 V V_{IN} = 0.0 V or V_{DD}	All	1, 3 1/		10	
				2 1/		600	
		V_{DD} = 20 V, V_{IN} = 0.0 V or V_{DD}	All	1		10	
				2		1000	
		M, D, P, L, R 2/	All	1		25	
		V_{DD} = 18 V, V_{IN} = 0.0 V or V_{DD}	All	3		10	
Low level output current (sink)	I_{OL}	V_{DD} = 5 V V_O = 0.4 V	All	1	0.53		mA
				2 1/	0.36		
				3 1/	0.64		
		V_{DD} = 10 V V_O = 0.5 V	All	1	1.4		
				2 1/	0.9		
				3 1/	1.6		
		V_{DD} = 15 V V_O = 1.5 V	All	1	3.5		
				2 1/	2.4		
				3 1/	4.2		
High level output current (source)	I_{OH}	V_{DD} = 5 V V_O = 4.6 V	All	1		-0.53	mA
				2 1/		-0.36	
				3 1/		-0.64	
		V_{DD} = 5 V V_O = 2.5 V V_O = 2.5 V	All	1		-1.8	
				2 1/		-1.15	
				3 1/		-2.0	
		V_{DD} = 10 V V_O = 9.5 V	All	1		-1.4	
				2 1/		-0.9	
				3 1/		-1.6	
		V_{DD} = 15 V V_O = 13.5 V	All	1		-3.5	
				2 1/		-2.4	
				3 1/		-4.2	

See footnotes at end of table.

TABLE IA. Electrical performance characteristics – Continued.

Test	Symbol	Test conditions $-55°C \le T_C \le +125°C$ unless otherwise specified	Device type	Group A subgroups	Limits		Units
					Min	Max	
Output voltage, high	V_{OH}	V_{DD} = 5 V, no load 1/	All	1, 2, 3	4.95		V
		V_{DD} = 10 V, no load 1/		1, 2, 3	9.95		
		V_{DD} = 15 V, no load 3/		1, 2, 3	14.95		
Output voltage, low	V_{OL}	V_{DD} = 5 V, no load 1/	All	1, 2, 3		50	mV
		V_{DD} = 10 V, no load 1/		1, 2, 3		50	
		V_{DD} = 15 V, no load		1, 2, 3		50	
Input voltage, low	V_{IL}	V_{DD} = 5 V V_{OH} > 4.5 V, V_{OL} < 0.5 V	All	1, 2, 3		1.5	V
		V_{DD} = 10 V V_{OH} > 9.0 V, V_{OL} < 1.0 V 1/		1, 2, 3		3	
		V_{DD} = 15 V V_{OH} > 13.5 V, V_{OL} < 1.5 V		1, 2, 3		4	
Input voltage, high	V_{IH}	V_{DD} = 5 V V_{OH} > 4.5 V, V_{OL} < 0.5 V	All	1, 2, 3	3.5		V
		V_{DD} = 10 V V_{OH} > 9.0 V, V_{OL} < 1.0 V 1/		1, 2, 3	7		
		V_{DD} = 15 V V_{OH} > 13.5 V, V_{OL} < 1.5 V		1, 2, 3	11		
Input leakage current, low	I_{IL}	V_{IN} = V_{DD} or GND, V_{DD} = 20 V	All	1	-100		nA
		V_{IN} = V_{DD} or GND, V_{DD} = 20 V		2	-1000		
		V_{IN} = V_{DD} or GND, V_{DD} = 18 V		3	-100		
Input leakage current, high	I_{IH}	V_{IN} = V_{DD} or GND, V_{DD} = 20 V	All	1		100	
		V_{IN} = V_{DD} or GND, V_{DD} = 20 V		2		1000	
		V_{IN} = V_{DD} or GND, V_{DD} = 18 V		3		100	
N threshold voltage	V_{NTH}	V_{DD} = 10 V, I_{SS} = -10 µA	All	1	-0.7	-2.8	V
		M, D, P, L, R 2/	All	1	-0.2	-2.8	
N threshold voltage, delta	ΔV_{NTH}	V_{DD} = 10 V, I_{SS} = -10 µA,	All	1		±1.0	
		M, D, P, L, R 2/					
P threshold voltage	V_{PTH}	V_{SS} = 0.0 V, I_{DD} = 10 µA	All	1	0.7	2.8	
		M, D, P, L, R 2/	All	1	0.2	2.8	
P threshold voltage, delta	ΔV_{PTH}	V_{SS} = 0.0 V, I_{DD} = 10 µA	All	1		±1.0	
		M, D, P, L, R 2/					
Input capacitance	C_{IN} 1/	Any input, See 4.4.1c	All	4		7.5	pF

See footnotes at end of table.

TABLE IA. Electrical performance characteristics – Continued.

Test	Symbol	Test conditions $-55°C \le T_C \le +125°C$ unless otherwise specified	Device type	Group A subgroups	Limits		Units
					Min	Max	
Functional tests		V_{DD} = 2.8 V, V_{IN} = V_{DD} or GND	All	7	V_{OH} > V_{DD}/2	V_{OL} < V_{DD}/2	V
		V_{DD} = 20 V, V_{IN} = V_{DD} or GND		7			
		V_{DD} = 18 V, V_{IN} = V_{DD} or GND	All	8A			
		M, D, P, L, R 2/	All	7			
		V_{DD} = 3.0 V, V_{IN} = V_{DD} or GND	All	8B			
		M, D, P, L, R 2/	All	7			
Transition time	t_{TLH}, t_{THL}	V_{DD} = 5.0 V, V_{IN} = V_{DD} or GND 4/	All	9		200	ns
				10, 11		270	
		V_{DD} = 10 V 1/ 4/		9		100	
		V_{DD} = 15 V 1/ 4/		9		80	
Propagation delay time, data to output	t_{PHL1}, t_{PLH1}	V_{DD} = 5.0 V, V_{IN} = V_{DD} or GND 4/	All	9		400	ns
				10, 11		540	
		M, D, P, L, R 2/	All	9		540	
		V_{DD} = 10 V 1/ 4/	All	9		150	
		V_{DD} = 15 V 1/ 4/		9		100	
Propagation delay time, write disable to output	t_{PHL2}, t_{PLH2}	V_{DD} = 5.0 V, V_{IN} = V_{DD} or GND 4/	All	9		400	ns
				10, 11		540	
		M, D, P, L, R 2/	All	9		540	
		V_{DD} = 10 V 1/ 4/	All	9		160	
		V_{DD} = 15 V 1/ 4/		9		120	
Propagation delay time, reset to output	t_{PHL3}	V_{DD} = 5.0 V, V_{IN} = V_{DD} or GND 4/	All	9		350	ns
				10, 11		473	
		M, D, P, L, R 2/	All	9		473	
		V_{DD} = 10 V 1/ 4/	All	9		160	
		V_{DD} = 15 V 1/ 4/		9		130	
Propagation delay time, address to output	t_{PHL4}, t_{PLH4}	V_{DD} = 5.0 V, V_{IN} = V_{DD} or GND 4/	All	9		450	ns
				10, 11		608	
		M, D, P, L, R 2/	All	9		608	
		V_{DD} = 10 V 1/ 4/	All	9		200	
		V_{DD} = 15 V 1/ 4/		9		150	

See footnotes at end of table.

TABLE IA. Electrical performance characteristics – Continued.

Test	Symbol	Test conditions $-55°C \le T_C \le +125°C$ unless otherwise specified	Device type	Group A subgroups	Limits		Units
					Min	Max	
Minimum hold time, data to write disable 1/ 4/	t_H	V_{DD} = 5.0 V	All	9		150	MHz
		V_{DD} = 10 V		9		75	
		V_{DD} = 15 V		9		50	
Minimum setup time, data to write disable 1/ 4/	t_S	V_{DD} = 5.0 V	All	9		100	ns
		V_{DD} = 10 V		9		50	
		V_{DD} = 15 V		9		35	
Minimum pulse width, data 1/ 4/	t_{WD}	V_{DD} = 5.0 V	All	9		200	ns
		V_{DD} = 10 V		9		100	
		V_{DD} = 15 V		9		80	
Minimum pulse width, address 1/ 4/	t_{WA}	V_{DD} = 5.0 V	All	9		400	ns
		V_{DD} = 10 V		9		200	
		V_{DD} = 15 V		9		125	
Minimum pulse width, reset 1/ 4/	t_{WR}	V_{DD} = 5.0 V	All	9		150	ns
		V_{DD} = 10 V		9		75	
		V_{DD} = 15 V		9		50	

1/ These tests are controlled via design or process and are not directly tested. These parameters are characterized on initial design release and upon design changes which affect these characteristics.

2/ RHA devices supplied to this drawing have been characterized through all levels M, D, P, L, and R of irradiation. However, these devices are only tested at the "R" level. Pre and post irradiation values are identical unless otherwise specified in table IA. When performing post irradiation electrical measurements for any RHA level, T_A = +25°C.

3/ For accuracy, voltage is measured differentially to V_{DD}. Limit is 0.050 V Max.

4/ C_L = 50 pF, R_L = 200kΩ, input t_r, t_f < 20 ns.

TABLE IB. SEP test limits. 1/ 2/

Device type	Single event upsets (SEU) Bias V_{DD} = 3.0 V	Single event latch-up (SEL) Bias V_{DD} = 3.0 V
	No SEU occurs at effective LET 3/ [MeV/(mg/cm^2)]	No SEL occurs at effective LET 3/ [MeV/(mg/cm^2)]
All	75	75

1/ For SEP test conditions, see 4.4.4.5 herein.
2/ Technology characterization and model verification supplemented by in-line data may be used in lieu of end-of-line testing. Test plan must be approved by TRB and qualifying activity.
3/ Guaranteed by design or process to a LET of = 75 MeV/(mg/cm^2) with no SEU and SEL.

Device type	01
Case outlines	E and X
Terminal number	Terminal symbol
1	Q7
2	RESET
3	DATA
4	WRITE DISABLE
5	A0
6	A1
7	A2
8	V_{SS}
9	Q0
10	Q1
11	Q2
12	Q3
13	Q4
14	Q5
15	Q6
16	V_{DD}

FIGURE 1. Terminal connections.

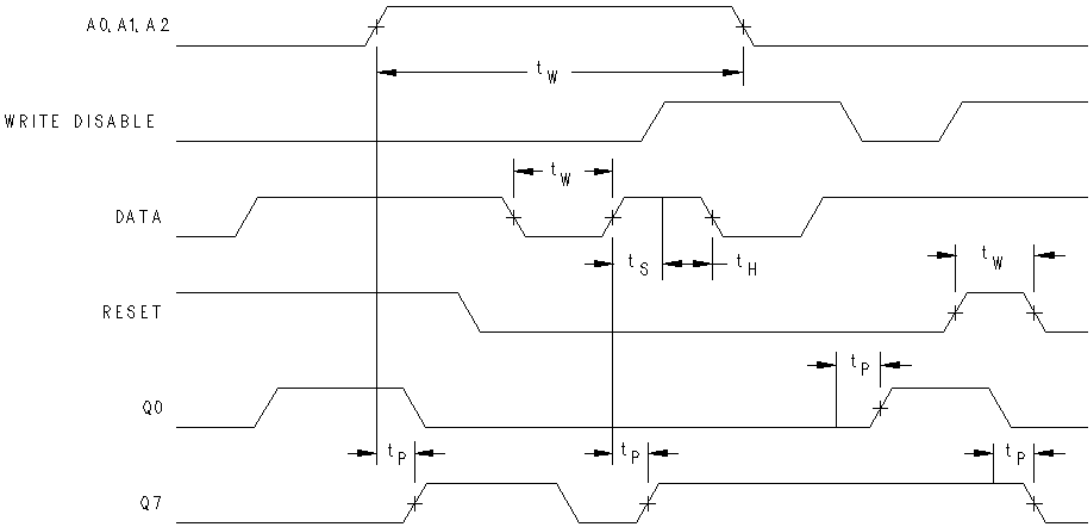


FIGURE 2. Timing diagram.

4. VERIFICATION

4.1 Sampling and inspection. For device classes Q and V, sampling and inspection procedures shall be in accordance with MIL-PRF-38535 or as modified in the device manufacturer's Quality Management (QM) plan. The modification in the QM plan shall not affect the form, fit, or function as described herein.

4.2 Screening. For device classes Q and V, screening shall be in accordance with MIL-PRF-38535, and shall be conducted on all devices prior to qualification and technology conformance inspection.

4.2.1 Additional criteria for device classes Q and V.

a. The burn-in test duration, test condition and test temperature, or approved alternatives shall be as specified in the device manufacturer's QM plan in accordance with MIL-PRF-38535. The burn-in test circuit shall be maintained under document revision level control of the device manufacturer's Technology Review Board (TRB) in accordance with MIL-PRF-38535 and shall be made available to the acquiring or preparing activity upon request. The test circuit shall specify the inputs, outputs, biases, and power dissipation, as applicable, in accordance with the intent specified in method 1015 of MIL-STD-883.

b. Interim and final electrical test parameters shall be as specified in table IIA herein.

c. Additional screening for device class V beyond the requirements of device class Q shall be as specified in MIL-PRF-38535, appendix B.

4.3 Qualification inspection for device classes Q and V. Qualification inspection for device classes Q and V shall be in accordance with MIL-PRF-38535. Inspections to be performed shall be those specified in MIL-PRF-38535 and herein for groups A, B, C, D, and E inspections (see 4.4.1 through 4.4.4).

4.4 Conformance inspection. Technology conformance inspection for classes Q and V shall be in accordance with MIL-PRF-38535 including groups A, B, C, D, and E inspections and as specified herein (see 4.4.1 through 4.4.4).

4.4.1 Group A inspection.

a. Tests shall be as specified in table IIA herein.

b. For device classes Q and V, subgroups 7 and 8 shall include verifying the functionality of the device.

c. Subgroup 4 (C_{IN} measurement) shall be measured only for the initial qualification and after process or design change which may affect capacitance. C_{IN} shall be measured between the designated terminal and GND at a frequency of 1 MHz. Tests shall be sufficient to validate the limits defined in table IA herein.

4.4.2 Group C inspection. The group C inspection end-point electrical parameters shall be as specified in table IIA herein.

4.4.2.1 Additional criteria for device classes Q and V. The steady-state life test duration, test condition and test temperature, or approved alternatives shall be as specified in the device manufacturer's QM plan in accordance with MIL-PRF-38535. The test circuit shall be maintained under document revision level control by the device manufacturer's TRB in accordance with MIL-PRF-38535 and shall be made available to the acquiring or preparing activity upon request. The test circuit shall specify the inputs, outputs, biases, and power dissipation, as applicable, in accordance with the intent specified in method 1005 of MIL-STD-883.

4.4.3 Group D inspection. The group D inspection end-point electrical parameters shall be as specified in table IIA herein.

TABLE IIA. Electrical test requirements.

Test requirements	Subgroups (in accordance with MIL-PRF-38535, table III)	
	Device class Q	Device class V
Interim electrical parameters (see 4.2)	1,7,9	1,7,9
Final electrical parameters (see 4.2)	1,2,3,7,8,9,10,11 1/	1,2,3,7,8,9,10,11 2/ 3/
Group A test requirements (see 4.4)	1,2,3,4,7,8,9,10,11	1,2,3,4,7,8,9,10,11
Group C end-point electrical parameters (see 4.4)	1,2,3,7,8,9,10,11	1,2,3,7,8,9,10,11 3/
Group D end-point electrical parameters (see 4.4)	1,7,9	1,7,9
Group E end-point electrical parameters (see 4.4)	1,7,9	1,7,9

1/ PDA applies to subgroups 1 and 7.
2/ PDA applies to subgroups 1, 7, 9, and deltas.
3/ Delta limits, as specified in table IIB, shall be required where specified, and the delta limits shall be completed with reference to the zero hour electrical parameters (see table IA).

TABLE IIB. Burn-in and operating life test, delta parameters (+25°C).

Parameter	Symbol	Delta limits
Supply current	I_{DD}	±1.0 μA
Output current (sink) V_{DD} = 5.0 V	I_{OL}	±20%
Output current (source) V_{DD} = 5.0 V, V_{OUT} = 4.6 V	I_{OH}	±20%

4.4.4 Group E inspection. Group E inspection is required only for parts intended to be marked as radiation hardness assured (see 3.5 herein).

a. End-point electrical parameters shall be as specified in table IIA herein.

b. For device classes Q and V, the devices or test vehicle shall be subjected to radiation hardness assured tests as specified in MIL-PRF-38535 for the RHA level being tested. All device classes must meet the postirradiation end-point electrical parameter limits as defined in table IA at T_A = +25°C ±5°C, after exposure, to the subgroups specified in table IIA herein.

4.4.4.1 Total dose irradiation testing. Total dose irradiation testing shall be performed in accordance with MIL-STD-883, method 1019, condition A, and as specified herein.

4.4.4.1.1 Accelerated annealing testing. Accelerated annealing tests shall be performed on all devices requiring a RHA level greater than 5k rads (Si). The post-anneal end-point electrical parameter limits shall be as specified in table IA herein and shall be the pre-irradiation end-point electrical parameter limits at 25°C ±5°C. Testing shall be performed at initial qualification and after any design or process changes which may affect the RHA response of the device.

4.4.4.2 Single event phenomena (SEP). When specified in the purchase order or contract, SEP testing shall be required on class V devices. SEP testing shall be performed on the Standard Evaluation Circuit (SEC) or alternate SEP test vehicle as approved by the qualifying activity at initial qualification and after any design or process changes which may affect the upset or latchup characteristics. Test four devices with zero failures. ASTM F1192 may be used as a guideline when performing SEP testing. The test conditions for SEP are as follows:

a. The ion beam angle of incidence shall be between normal to the die surface and 60° to the normal, inclusive (i.e. 0° ≤ angle ≤ 60°). No shadowing of the ion beam due to fixturing or package related effects is allowed.

b. The fluence shall be ≥ 100 errors or ≥ 10^7 ions/cm^2.

c. The flux shall be between 10^2 and 10^5 ions/cm^2/s. The cross-section shall be verified to be flux independent by measuring the cross-section at two flux rates which differ by at least an order of magnitude.

d. The particle range shall be ≥ 20 microns in silicon.

e. The upset test temperature shall be +25°C and the latchup test temperature is maximum rated operating temperature 10°C.

f. Bias conditions shall be defined by the manufacturer for latchup measurements.

g. For SEP test limits, see table IB herein.

4.5 Methods of inspection. Methods of inspection shall be as specified as follows:

4.5.1 Voltage and current. Unless otherwise specified, all voltages given are referenced to the microcircuit GND terminal. Currents given are conventional current and positive when flowing into the referenced terminal.

5. PACKAGING

5.1 Packaging requirements. The requirements for packaging shall be in accordance with MIL-PRF-38535 for device classes Q and V.

6. NOTES

6.1 Intended use. Microcircuits conforming to this drawing are intended for use for Government microcircuit applications (original equipment), design applications, and logistics purposes.

6.1.1 Replaceability. Microcircuits covered by this drawing will replace the same generic device covered by a contractor-prepared specification or drawing.

6.2 Configuration control of SMD's. All proposed changes to existing SMD's will be coordinated with the users of record for the individual documents. This coordination will be accomplished using DD Form 1692, Engineering Change Proposal, or email communication.

6.3 Record of users. Military and industrial users should inform DLA Land and Maritime when a system application requires configuration control and which SMD's are applicable to that system. DLA Land and Maritime will maintain a record of users and this list will be used for coordination and distribution of changes to the drawings. Users of drawings covering microelectronic devices (FSC 5962) should contact DLA Land and Maritime -VA, telephone (614) 692-8108.

6.4 Comments. Comments on this drawing should be directed to DLA Land and Maritime -VA, Columbus, Ohio 43218-3990, or telephone (614) 692-0591.

6.5 Abbreviations, symbols, and definitions. The abbreviations, symbols, and definitions used herein are defined in MIL-PRF-38535 and MIL-HDBK-1331.

6.6 Source of supply.

6.6.1 Sources of supply for device classes Q and V. Sources of supply for device classes Q and V are listed in MIL-HDBK-103 and QML-38535. The vendors listed in MIL-HDBK-103 and QML-38535 have submitted a certificate of compliance (see 3.6 herein) to DLA Land and Maritime -VA and have agreed to this drawing.

6.7 Additional information. A copy of the following additional data shall be maintained and available from the device manufacturer:

a. RHA test conditions (SEP).

b. Number of upsets (SEU).


c. Number of transients (SET).

d. Occurrence of latch-up (SEL).

A.1 SCOPE

A.1.1 Scope. This appendix establishes minimum requirements for microcircuit die to be supplied under the Qualified Manufacturers List (QML) Program. QML microcircuit die meeting the requirements of MIL-PRF-38535 and the manufacturers approved QM plan for use in monolithic microcircuits, multi-chip modules (MCMs), hybrids, electronic modules, or devices using chip and wire designs in accordance with MIL-PRF-38534 are specified herein. Two product assurance classes consisting of military high reliability (device class Q) and space application (device Class V) are reflected in the Part or Identification Number (PIN). When available a choice of Radiation Hardness Assurance (RHA) levels is reflected in the PIN.

A.1.2 PIN. The PIN is as shown in the following example:

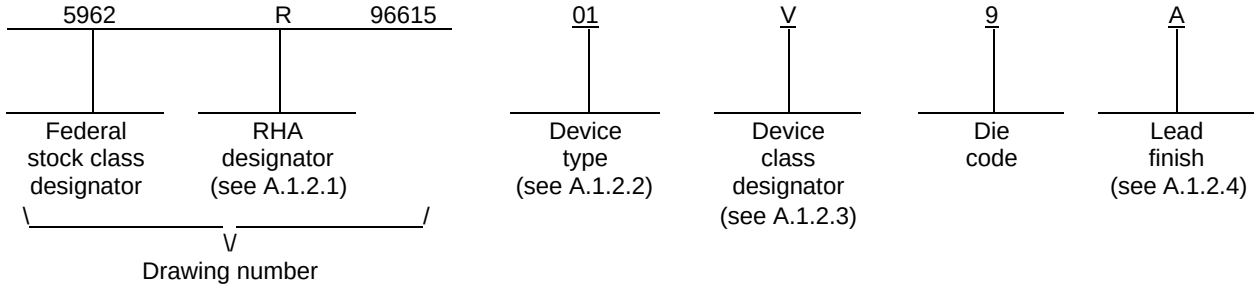

A.1.2.1 RHA designator. Device classes Q and V RHA identified die shall meet the MIL-PRF-38535 specified RHA levels. A dash (-) indicates a non-RHA die.

A.1.2.2 Device type(s). The device type(s) shall identify the circuit function as follows:

Device type	Generic number	Circuit function
01	4099B	Radiation hardened, CMOS, 8-bit addressable latch

A.1.2.3 Device class designator.

Device class	Device requirements documentation
Q or V	Certification and qualification to the die requirements of MIL-PRF-38535

A.1.2.4 Die Details. The die details designation shall be a unique letter which designates the die's physical dimensions, bonding pad location(s) and related electrical function(s), interface materials, and other assembly related information, for each product and variant supplied to this appendix.

A.1.2.4.1 Die physical dimensions.

Die types	Figure number
01	A-1

A.1.2.4.2 Die bonding pad locations and electrical functions.

Die types	Figure number
01	A-1

A.1.2.4.3 Interface materials.

Die types	Figure number
01	A-1

A.1.2.4.4 Assembly related information.

Die types	Figure number
01	A-1

A.1.3 Absolute maximum ratings. See paragraph 1.3 herein for details.

A.1.4 Recommended operating conditions. See paragraph 1.4 herein for details.

A.2 APPLICABLE DOCUMENTS.

A.2.1 Government specification, standards, and handbooks. The following specification, standards, and handbooks form a part of this drawing to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

DEPARTMENT OF DEFENSE SPECIFICATION

MIL-PRF-38535 - Integrated Circuits, Manufacturing, General Specification for.

DEPARTMENT OF DEFENSE STANDARD

MIL-STD-883 - Test Method Standard Microcircuits.

DEPARTMENT OF DEFENSE HANDBOOKS

MIL-HDBK-103 - List of Standard Microcircuit Drawings.
MIL-HDBK-780 - Standard Microcircuit Drawings.

(Copies of these documents are available online at https://quicksearch.dla.mil/.)

A.2.2 Order of precedence. In the event of a conflict between the text of this drawing and the references cited herein, the text of this drawing takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

A.3 REQUIREMENTS

A.3.1 Item requirements. The individual item requirements for device classes Q and V shall be in accordance with MIL-PRF-38535 and as specified herein or as modified in the device manufacturer's Quality Management (QM) plan. The modification in the QM plan shall not effect the form, fit or function as described herein.

A.3.2 Design, construction and physical dimensions. The design, construction and physical dimensions shall be as specified in MIL-PRF-38535 and the manufacturer's QM plan, for device classes Q and V and herein.

A.3.2.1 Die physical dimensions. The die physical dimensions shall be as specified in A.1.2.4.1 and on figure A-1.

A.3.2.2 Die bonding pad locations and electrical functions. The die bonding pad locations and electrical functions shall be as specified in A.1.2.4.2 and on figure A-1.

A.3.2.3 Interface materials. The interface materials for the die shall be as specified in A.1.2.4.3 and on figure A-1.

A.3.2.4 Assembly related information. The assembly related information shall be as specified in A.1.2.4.4 and figure A-1.

A.3.2.5 Radiation exposure circuit. The radiation exposure circuit shall be as defined in paragraph 3.2.4 herein.

A.3.3 Electrical performance characteristics and post-irradiation parameter limits. Unless otherwise specified herein, the electrical performance characteristics and post-irradiation parameter limits are as specified in table IA of the body of this document.

A.3.4 Electrical test requirements. The wafer probe test requirements shall include functional and parametric testing sufficient to make the packaged die capable of meeting the electrical performance requirements in table IA.

A.3.5 Marking. As a minimum, each unique lot of die, loaded in single or multiple stack of carriers, for shipment to a customer, shall be identified with the wafer lot number, the certification mark, the manufacturer's identification and the PIN listed in A.1.2 herein. The certification mark shall be a "QML" or "Q" as required by MIL-PRF-38535.

A.3.6 Certification of compliance. For device classes Q and V, a certificate of compliance shall be required from a QML-38535 listed manufacturer in order to supply to the requirements of this drawing (see 60.4 herein). The certificate of compliance submitted to DLA Land and Maritime-VA prior to listing as an approved source of supply for this appendix shall affirm that the manufacturer's product meets, for device classes Q and V, the requirements of MIL-PRF-38535 and the requirements herein.

A.3.7 Certificate of conformance. A certificate of conformance as required for device classes Q and V in MIL-PRF-38535 shall be provided with each lot of microcircuit die delivered to this drawing.

A.4 VERIFICATION

A.4.1 Sampling and inspection. For device classes Q and V, die sampling and inspection procedures shall be in accordance with MIL-PRF-38535 or as modified in the device manufacturer's Quality Management (QM) plan. The modifications in the QM plan shall not affect the form, fit, or function as described herein.

A.4.2 Screening. For device classes Q and V, screening shall be in accordance with MIL-PRF-38535, and as defined in the manufacturer's QM plan. As a minimum, it shall consist of:

a. Wafer lot acceptance for class V product using the criteria defined in MIL-STD-883, method 5007.

b. 100% wafer probe (see paragraph A.3.4 herein).

c. 100% internal visual inspection to the applicable class Q or V criteria defined in MIL-STD-883, method 2010 or the alternate procedures allowed in MIL-STD-883, method 5004.

A.4.3 Conformance inspection.

A.4.3.1 Group E inspection. Group E inspection is required only for parts intended to be identified as radiation assured (see A.3.5 herein). RHA levels for device classes Q and V shall be as specified in MIL-PRF-38535. End point electrical testing of packaged die shall be as specified in table IIA herein. Group E tests and conditions are as specified in paragraphs 4.4.4 herein.

A.5 DIE CARRIER

A.5.1 Die carrier requirements. The requirements for the die carrier shall be accordance with the manufacturer's QM plan or as specified in the purchase order by the acquiring activity. The die carrier shall provide adequate physical, mechanical and electrostatic protection.


A.6 NOTES

A.6.1 Intended use. Microcircuit die conforming to this drawing are intended for use in microcircuits built in accordance with MIL-PRF-38535 or MIL-PRF-38534 for government microcircuit applications (original equipment), design applications and logistics purposes.

A.6.2 Comments. Comments on this appendix should be directed to DLA Land and Maritime-VA, Columbus, Ohio, 43218-3990 or telephone (614) 692-0591.

A.6.3 Abbreviations, symbols and definitions. The abbreviations, symbols, and definitions used herein are defined in MIL-PRF-38535 and MIL-HDBK-1331.

A.6.4 Sources of supply for device classes Q and V. Sources of supply for device classes Q and V are listed in MIL-HDBK-103 and QML-38535. The vendors listed within MIL-HDBK-103 and QML-38535 have submitted a certificate of compliance (see A.3.6 herein) to DLA Land and Maritime-VA and have agreed to this drawing.

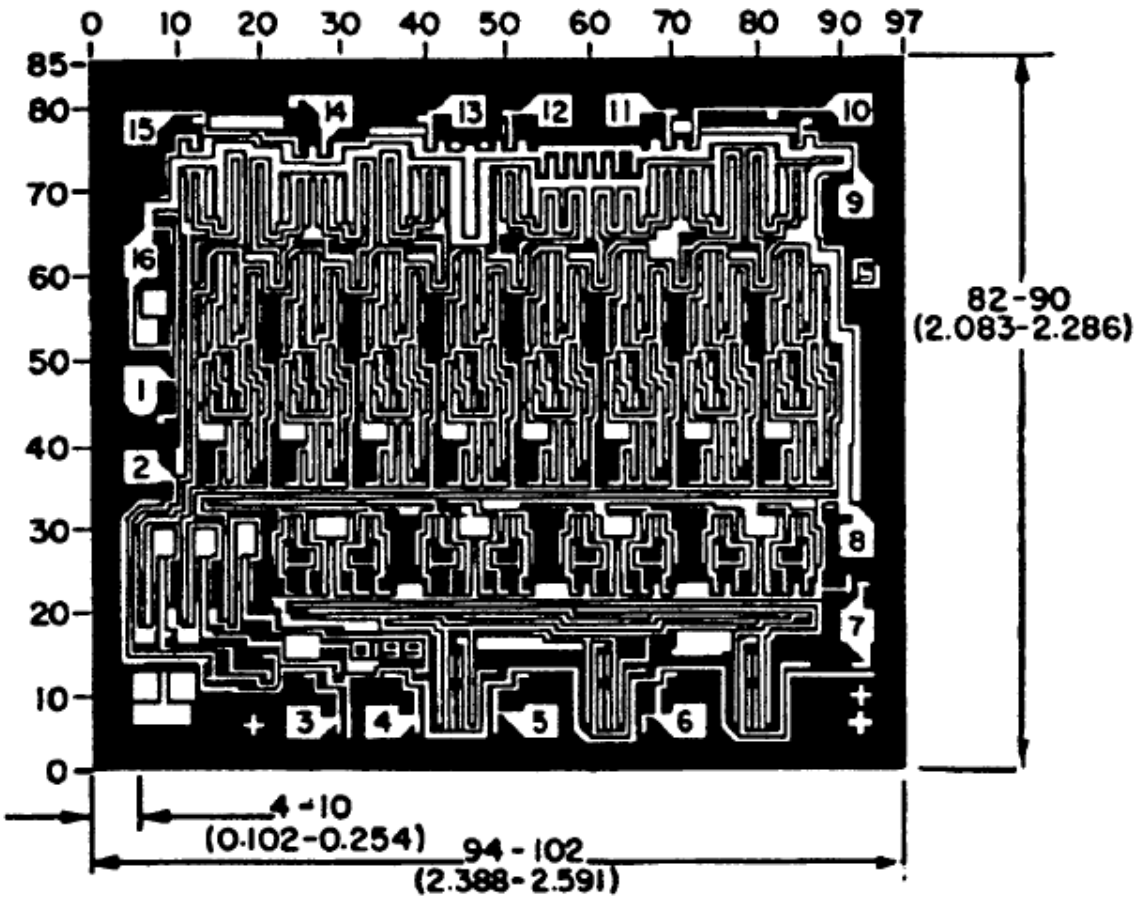

NOTE: Pad numbers reflect terminal numbers when placed in case outlines E and X (see figure 1).

FIGURE A-1. Die bonding pad locations and electrical functions.

Die physical dimensions.

Die size:	2159 x 2464 microns
Die thickness:	20 ±1 mils

Interface materials.

Top metallization:	Al
Thickness:	11.0kÅ - 14.0kÅ
Backside metallization:	None

Glassivation.

Type:	PSG
Thickness:	10.4kÅ - 15.6kÅ

Substrate: Single Crystal Silicon

Assembly related information.

Substrate potential:	Floating or tied to V_{DD}
Special assembly instructions:	Bond pad #16 (V_{DD}) first.

FIGURE A-1. Die bonding pad locations and electrical functions – Continued.

STANDARD MICROCIRCUIT DRAWING BULLETIN

DATE: 23-04-14

Approved sources of supply for SMD 5962-96615 are listed below for immediate acquisition information only and shall be added to MIL-HDBK-103 and QML-38535 during the next revision. MIL-HDBK-103 and QML-38535 will be revised to include the addition or deletion of sources. The vendors listed below have agreed to this drawing and a certificate of compliance has been submitted to and accepted by DLA Land and Maritime-VA. This information bulletin is superseded by the next dated revision of MIL-HDBK-103 and QML-38535. DLA Land and Maritime maintains an online database of all current sources of supply at https://landandmaritimeapps.dla.mil/programs/smcr/.

Standard microcircuit drawing PIN 1/	Vendor CAGE number	Vendor similar PIN 2/
5962R9661501VEC	34371	CD4099BDMSR
5962R9661501VXC	34371	CD4099BKMSR
5962R9661501V9A	34371	CD4099BHSR

1/ The lead finish shown for each PIN representing a hermetic package is the most readily available from the manufacturer listed for that part. If the desired lead finish is not listed contact the vendor to determine its availability.

2/ Caution. Do not use this number for item acquisition. Items acquired to this number may not satisfy the performance requirements of this drawing.

Vendor CAGE number	Vendor name and address
34371	Renesas Electronics America, Inc. 1650 Robert J. Conlan Blvd. NE Palm Bay, FL 32905-3406

The information contained herein is disseminated for convenience only and the Government assumes no liability whatsoever for any inaccuracies in the information bulletin.